

DUCTILE IRON PIPE SURFACE CHARACTERIZATION AND PINHOLE FORMATION

**Prof. Dr. Fevzi YILMAZ,
Özgür CEVHER (M.Sc.) and Mustafa BAYRAKTAR (M.Sc.)**

University of Sakarya, Department of Metallurgical and Materials Engineering, Esentepe
Campus, 54187 Adapazarı, TURKEY
Email: yilmazf@sakarya.edu.tr

ABSTRACT

Manufacturing defects play a large role in the failure of pipes. A pipe will fail if it is not manufactured properly. Changing of wall thickness and composition, and availability of surface defects such as pinholes (very small holes scattered throughout the casting) are important headache for manufacturers as well as users of pipes.

Casting with pinholes is very common at centrifugal casting processes. When procedures aren't followed with care, pinholes can be serious defect on ductile iron pipes. These pinholes are usually either isolated or few in number, and frequently located at the outer surface. Since ductile iron pipes are generally used as as-cast and heat treated conditions, surface structure and surface oxidation also become important. Annealing oxide provides some degree of corrosion protection. This study explains the dynamics involved in surface defects such as pinhole variation, and details on how this problem can be eliminated.

Keywords: Centrifugal casting, Ductile iron pipe, Surface defects, Pinholes, Oxides

1. INTRODUCTION

It is well known fact that ductile iron pressure pipes are produced by centrifugal casting in industry. The De Lavaud process is the main manufacturing method used worldwide for large castings [1]. The casting machine consists of a cylindrical steel mould surrounded by a water jacket and is mounted on rollers, so that it can be rotated. The entire assembly, jacket and mould, can be moved longitudinally and facilitates to produce long (≈ 6 m) and big diameter (100 mm to 2000 mm) pipes. Centrifugal castings have many of the same defects as static castings but are far less prone to them. Cold shots due to unmelted globules, penetration (dips) due to mould coating, cold shuts (laps) due to misrun and pinholes (blowholes) due to moisture can be observed on pipe surface, if it is not manufactured properly. There is, however, a pronounced absence of haphazard internal shrinkage and inclusion in centrifugal castings.

Some of the defects, including surface oxide layers can be removed by sand blasting and machining. Since ductile iron pipes are generally used as as-cast condition, unique surface structure becomes important. If, specifications indicate surface coatings (Zn, Zn/Al, epoxy, bitumen, PE etc.) are applied on pipes for protection or seal.

Recent corrosion studies [2-4] indicated the importance of surface conditions of the pipes. Bare pipe shows better performance than sand blasted one. A typical continuous annealing oxide provides some degree of corrosion protection for ductile iron pipe.

According to UK Water Industry Research (UKWIR) report, pinholes in ductile iron pipes have an important role for defect formation and pipe failure [5]. During the usage, if as cast pinhole defects are available, they deepen and penetrate all over the pipe width. Corrosion pinholes which formed later are out of scope of this article.

Yamabe and Kobayashi [6] studied the effect of pinholes on fatigue behavior of castings. They concluded that pinholes and layers around pinholes initiate the fracture. The size and the number of pinholes significantly lower the fatigue strength as well as total performance of the casting. Obviously, this is important for pipes which are under cycling traffic load and water hammering.

Cast iron mostly has a liquid film composed of a low melting point mix of oxides [7]. On entrainment of the surface the liquid film joins to the other folded over liquid film and immediately coalesces, forms droplets and floats out. Thus cast irons can be particularly free of problems. In ductile iron, Magnesium vapor distills off through dross since the molten alloy is above the boiling point of Mg. Small irregularly shaped graphite spheroids and possibly malformed spheroids form as a result of local loss of Mg. Liquid films can easily move out at centrifuging and there are no internal oxide problems in both of the irons. As it is expected, ductile iron pipe goes to annealing treatment after casting and thick layer of surface oxides form.

Oxide layer on the surface protects the ductile iron from corrosion if it is continuous and smooth. If there is discontinuity of iron oxides, no protective value is experienced and pitting corrosion develops [7].

Pinholes are likely to occur on thinner pipe. Holes can be caused by an excessively high or low pouring temperature. One common cause of pinholes is moisture retained in the mould coating or some constituent of the coating that turns to a gas when the molten metal comes into contact with it. This gas, as well as gas generated from internal source of melt tends to migrate and the easiest path, in most cases, is through the molten metal. Surface and subsurface pinhole grows in competition with solid layer, into melt. The pore gains gas from the surface reaction, and loses it from its growing front. If growing front is entrapped by solid layer or if the surface of pinhole is covered by oxide, smooth pore shape becomes curved and twisted. However, when the molten metal is in the process of quick solidification and first solid layer forms immediately, the gas will become entrapped, curved as they emerge from the coating (Fig 1). Since layer formation rate or growth rate is very high in centrifugal casting (hundreds of $\mu\text{m}/\text{sec}$ in centrifugal castings, tents of $\mu\text{m}/\text{sec}$ in sand casting) cylindrical surface pinholes generally develop on pipes (Fig 2).

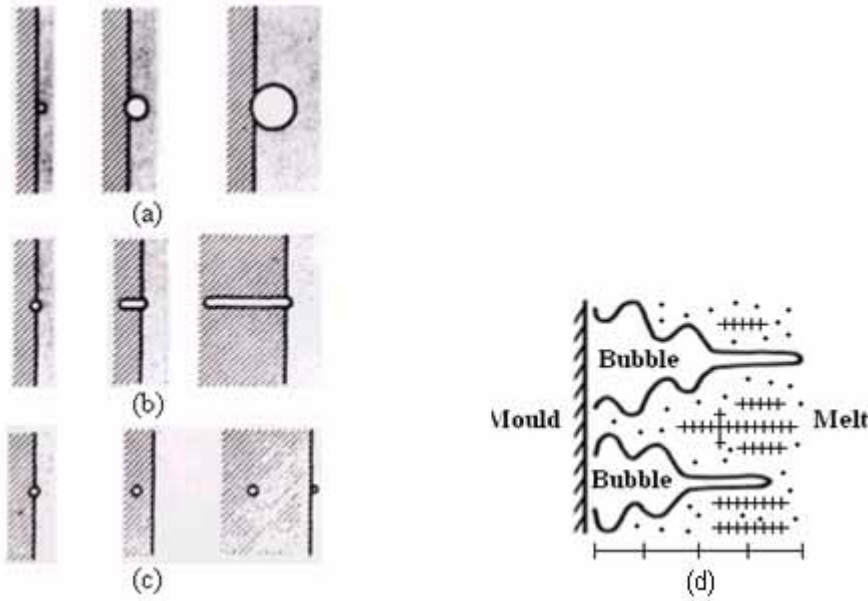


Figure 1. Pinhole formation [12]. a) Slow growth rate of solid layers. Bubble can move with the interface behavior of pushing (no pinhole left in the casting). b) Intermediate growth of solid layer. Bubble can become incorporated into the interface to grow as an elongated pinhole (surface pinholes on casting). c) Fast growth of solid layer. Surface entrapment of pinholes which can be rapidly overgrown by the interface (small holes separated in casting). d) Sketch drawn at present work. Surface pores growing together from a mould surface of high gas content in centrifugal casting. Growing front elongates into a melt.

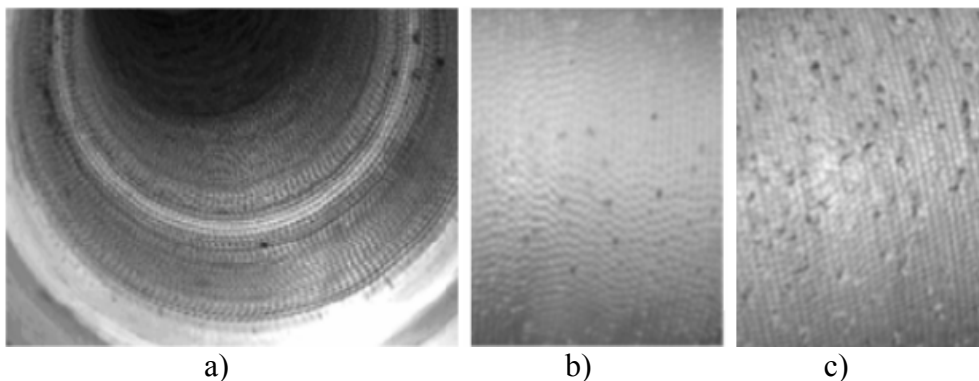


Figure 2. Steel mould (a) and ductile iron pipes (b-c) produced centrifugally. a) Steel mould with internal wavy zone to hold solidifying pipe. b) Surface of pipe produced under very high molten metal temperature (Moulds internal wavy zone pass to pipe surface. Pin pointing pinholes are clear). c) Surface of pipe produced under very low molten metal temperature (Moulds internal wavy zone can hardly be seen on the pipe. Curved cylindrical pinholes are clear).

Corrective measures include elimination of gassing possibilities; use of an exothermic pipe eliminator to promote unidirectional solidification and the appropriate pouring temperature possible without causing cold shuts. Shortly, pinhole defects can be avoided by taking below given precautions:

- a) Making the mould carefully and maintaining its temperature accurately,
- b) Using coating materials that contain less volatile mixture, less moisture and no free water of crystallization,
- c) Maintaining an accurate molten metal temperature,
- d) Taking the relatively high mould rotation speed.

Pinholes or pinhole defects may be categorized as entrapped, aspiration, evolution, reaction or other pinhole types. This article deals specifically with entrapped pinholes generally associated with mould coating volatiles and moistures. Surface oxide layers and protective values of them are also searched.

2. EXPERIMENTAL PROCEDURES

The materials used for pinhole and surface oxidation study were GGG 40 grade ductile irons which were cast in steel mould water cooled De Lavoud type centrifugal casting machine. Normally, defect-free pipes are in production as long as process parameters such as melting condition, flowing rate, rotation speed and temperature, etc. are strictly followed. In production plant first a few pipes produced can have pinholes since process parameters can not be controlled (Fig. 2). In all production runs, pinhole occurrence was most severe in the first ladle of the run since initial pouring and moulding conditions are variable. One of such pipes DN100 (118mm OD, 106mm ID) was taken and rings were cut to examine the defects and surfaces (Fig. 3a).

Surface topography, number, shape, volume fraction of pinholes in given area were examined. The specimens with machined layers up to 2mm of depth removed from surface gradually and at each stage pinholes were examined. One of the ductile iron pipe ring which has much pronounced pinholes are given in Fig 3a. Fig. 3(b-d) shows changing of surface topography due to machining.

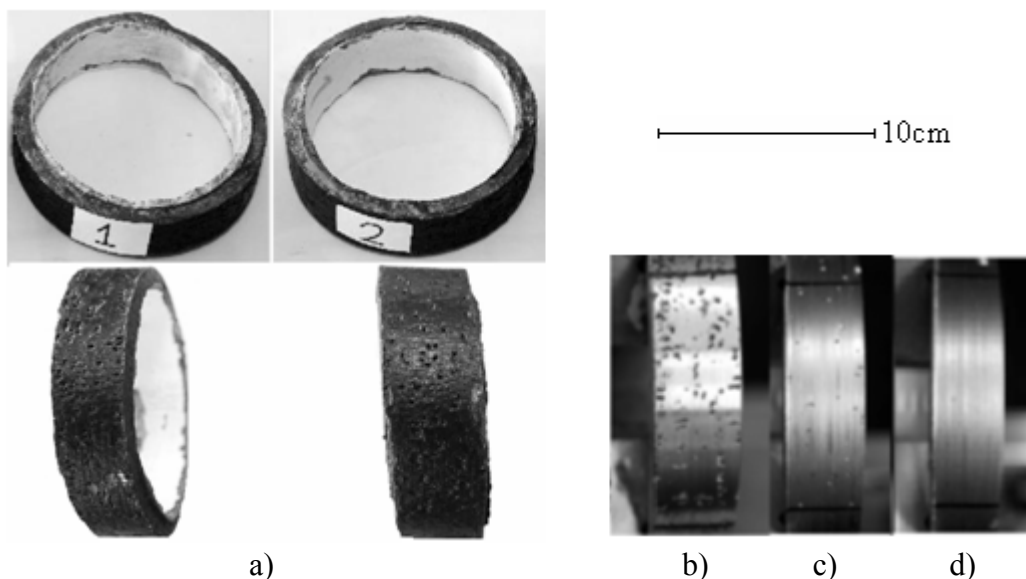


Figure 3. Pinhole rich pipe rings and surface machining. a) Four ductile iron pipe ring samples (6mm alloy wall thickness, 3mm internal cement lining and external bitumen paint are evident. Note that under the bitumen paint thin zinc coating and surface iron oxide are available. b) 0,5mm depth machining, c) 1mm depth machining, d) 1,5mm depth machining.

Results were graphed and statistically analyzed using the procedure outlined in Design and Analysis of Experiments. Pinhole numbers by point counting and total surface area of pinholes by line intercept were measured on as-cast and machined surfaces.

Changing the structure towards the surface, around the pinholes and chemical composition were searched by optical and SEM microscopy as well as EDS techniques. The hardness of

matrix structure, oxide layers and the structure close to pinhole were measured by using a Vickers hardness tester. The hardness was measured at 10 points under a load of 100 gr.

3. RESULT AND DISCUSSION

It is believed that during centrifugal casting, when ductile iron liquid is hot enough or mould temperature is high, thin Fe layer develops at early stage. Entrapped gas which is between the mould and liquid moves towards liquid and escapes from inner surface of the pipe (Fig. 1). Sometimes small canal which transfer the gas throughout the pipe forms. The wall of the canal can be covered by thin and fragmented oxide layer. SEM study showed thick iron oxide layer of the canal after annealing (Fig. 4). If the first solid layer formed on the mould is thick enough under the condition of low liquid metal temperature (or cold mould), entrapped gas can't move inside towards the pipe wall. Entrapped gas amount and pressure increase by the time and lateral curved gas hole develops. Curved, dendrite or conical shape is evidenced during experimentation. As given Fig. 6, pinhole length is as long as 1.7mm which is too much and unacceptable. Gradual decrease of number of pinholes with depth is understandable. Step reduction of volume ratio with depth implies conical shape of pinholes as sketched in Fig. 1d.

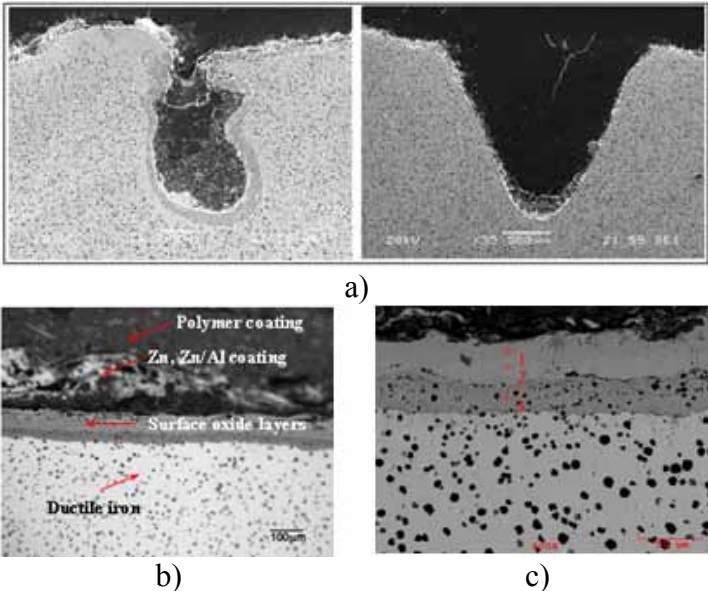


Figure 4. Pinholes and oxide layers (SEM pictures) a) Shape and depth of pinholes in transverse section. b) Oxide layers on surface without pinhole. c) Oxide layers on pinhole edge. All pictures were taken after annealing treatment.


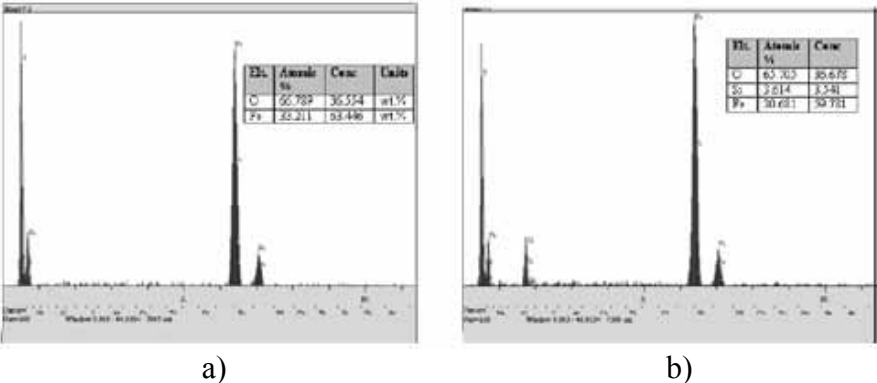


Figure 5. EDS pattern of sample given in Figure 4c. a) Point 2, b) Point 3

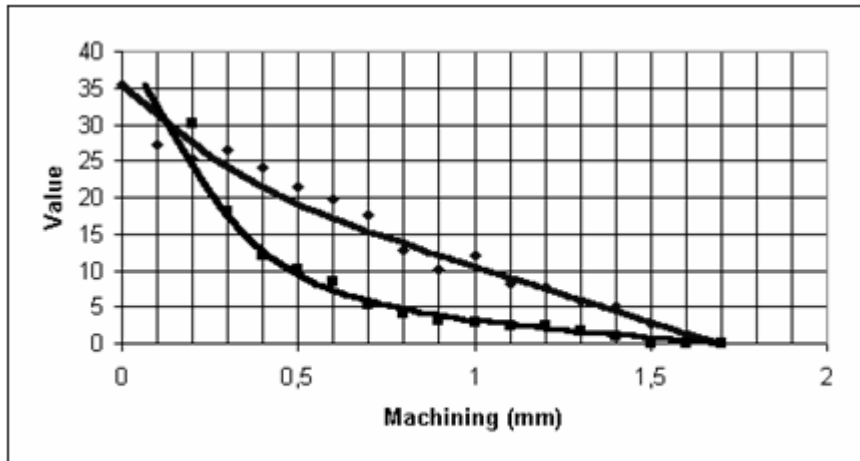

■ — Pinhole Volume Fraction (%)
 ◆ — Number of Pinhole (N/1000mm²)

Figure 6. Changing the number and volume fraction of pinholes with machining depth from the surface.

Optical and SEM microscopy study showed that ductile iron surface layer developed is nearly pure iron which is very ductile and easily deformed due to gas pressure. If conditions prevail gas penetrates inside from this hot iron layer. Iron film can be oxidized most probably at the lateral stages of solidification (Fig. 7) and during annealing (Fig. 4 and 8). Rarely, fragmented oxide films observed on the surfaces of ductile iron pipes. It is clear from Fig. 8 that oxide film is rather thick, if the heating temperature is high and period is long enough (~950°C, ~1h).

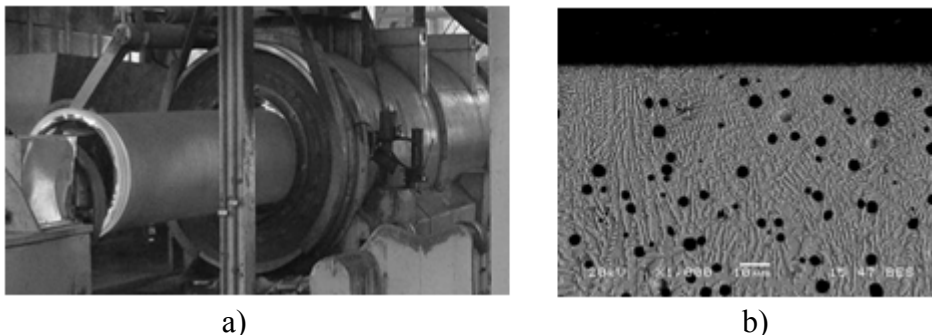


Figure 7. As-cast ductile iron pipe surface a) Hot surface of pipe during the removal from centrifugal casting machine. b) SEM microstructure of heavily etched surface and internal section as-cast ductile iron pipe (Before annealing). Spherical graphite and carbide-rich matrix are evident. Top end of cast surface is covered by oxide film with a few micrometer thicknesses.

Around pinholes and on all the surfaces three oxide layers were recognized but there were no clear boundary between the layers (Fig. 8). EDS tests supported these findings. While outer surface layer is oxygen rich, the layer nearby ductile matrix is oxygen poor. Total thickness of oxide layer was approximately 80 μm. The thicknesses of each layer were more or less equal. Fragmented surface oxides and other two layers with color differences can be seen in Fig. 4 and 8. EDS analysis is given in Fig. 5. Present result was compared with previous findings [8-10]. The research study made by Horn [10] measured total thickness of 143 μm with similar layers and structures observed at present research. Rather low thickness experienced in present work is due to different heat treatment and temperature.

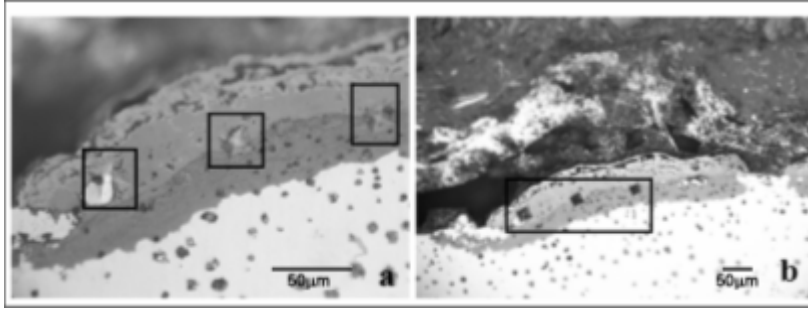


Figure 8. Layers of annealing oxides and indenter traces. Mean values (HV): ductile iron substrate (below matrix)= 240 ± 15 , inner oxide layer(right trace)= 480 ± 25 , middle oxide layer(middle trace)= 380 ± 27 and top oxide layer(left trace)= 320 ± 40 .

The hardness tests gave different values in different layers. Although, big hardness deviation was available in each layer, there are clear differences in morphology and hardness of layers as expected. Since oxide layer thickness was so small and upper layer was rather fragmented, taking the accurate measurement was difficult. Hardness of oxide in first layer was approximately 480HV which is 2 times higher than ductile iron matrix (240HV).

Previous study [11] on steel indicates that the first oxide layer adjacent to matrix is magnetite (Fe_3O_4). Annealed steel surface oxide bonding to matrix is relatively weak. Ductile iron annealing surface first oxide layer is Fe, Si, O rich and has good bonding (Fig. 4 and 8). In steel because the different coefficient of expansion between the substrate (steel base) and the oxide cause the scale to become detached [11]. However, in ductile iron, it is believed that availability of silicon in matrix is helped the formation of good bonding.

4. CONCLUSIONS

Using today's state of the art ductile iron processing, foundries can produce castings with a very low incidence of pinhole defects. The best results are obtained when melting and pouring is controlled carefully. In addition to these, the centrifugal casting needs proper adjustment of mould temperature, mould coating and mould rotation. When procedures aren't followed with care, pinholes can be serious defect on ductile iron pipes produced by centrifugal casting.

Liquid metal composition (like Al, Mg levels) and availability of gas forming elements (H, N, O) in liquid affect pinhole formation. Pinholes develop due to internal effects move inside the pipe and escape. Solidification dynamics are involved in the centrifugal casting. Main cause of pinhole in this process is generally mould coating and parameters of centrifuging. Surface pinholes with curved cylinder and dendrite shape can penetrate to the pipe from surface to one fourth of the cross section. Pinhole defects can be avoided by maintaining liquid-mould temperature accurately, using coating materials that contain less volatile mixture-less moisture and taking the relatively high mould rotation speed.

As-cast ductile iron pipe surface has both casting oxide and thick annealing oxide. The abrasive blast surface preparation is not economical and negates the protective effects from resulting from annealing oxide. It is observed that bonding between oxide layer and ductile iron matrix is relatively good and continuous. 3 easily detectable oxide layers cover all the surfaces of pipes as well as pinhole pools. It is believed that first layer above ductile iron matrix has remarkably good protective value against corrosion.

Acknowledgement: The work reported here is part of a research project on “105M061 High Performance Thermal Spray Coatings”. The financial support by TUBITAK (The Scientific And Technological Research Council of Turkey) and materials supply by ISKI (Istanbul Water And Sewerage Administration) are gratefully acknowledged.

5. REFERENCES

- [1] N. Janco, “Centrifugal Casting”, American Foundrymen’s Society Inc., Illionis, 1992
- [2] D.H. Kroon, D. Lindemuth, S. Sampson, T. Vincenzo, “Corrosion protection of ductile iron pipe”, pp: 24-29, Materials Performance, January 2005
- [3] R.W. Bonds, A.M. Horton, G.L. Oliver, L.M. Barnard, “Corrosion control statistical analysis of iron pipe”, 30-34, Materials Performance, January 2005
- [4] M.J. Szeliga and D. M. Simpson, “Evaluating ductile iron pipe corrosion”, 22-27, Materials Performance, July 2003
- [5] <http://etd.rau.ac.za/theses/available/etd-10042006-085426/restricted/Chapter2.pdf>
- [6] J. Yamabe, M. Kobayashi, “Influence of casting surface on fatigue strength of ductile iron”, Fatigue Fracture Engineering Materials Structure 29, 403-415, 2006
- [7] J.Campbell, “Castings”, 2nd ed. 2003, Oxford, Butterworth-Heinemann Ltd.
- [8] R. W. Heine, E. R. Kaczmarek, M. Rothwell, R. Leitermann, “ ‘Pin-pointing’ ductile iron pihole and slag defects”, Modern casting, 32-35, August 1997
- [9] D.H. Kroon, D. Lindemuth, S. Sampson, and Terry Vincenzo, “Corrosion protection of ductile iron pipe”, Materials Performance, 24-29, January 2005
- [10] L.G. Horn, “The design decision model for corrosion control of ductile iron pipelines”, www.dipra.org
- [11] S.Birosca, D.Dingley and R.L.Hingsinson, “Microstructural and microtextural characterization of oxide scale on steel using electron backscatter diffraction”, Journal of Microscopy, 235-240, Vol 213, 3 March 2004.
- [12] G.J.Daves; “Solidifation and Casting”, 91, 1973 London, Applied Science Publishers